



# GRANULOMETRIA DE AGREGADO 78

|                   |                        |
|-------------------|------------------------|
| Planta: Huayco    | Codigo: SI-RG-010-10-7 |
| Realizado: M.A.R. | Fecha: 2018-08-31      |
| Revisado: E.W.P.  | Aprobado: V.B.D.       |
| Edición: 00       | Página: 1 de 1         |


INEN 696 - ASTM D448

|                   |             |
|-------------------|-------------|
| FECHA DE ENSAYO:  | 2018-08-31. |
| FECHA DE ENTREGA: |             |
| PROCEDENCIA:      | STOCK       |
| MASA INICIAL:     | 3,025.60    |

| TAMIZ INEN - ASTM | MASA RETENIDA (g) | % RETENIDO PARCIAL | % RETENIDO ACUMULADO | % PASANTE ACUMULADO | NORMA   |
|-------------------|-------------------|--------------------|----------------------|---------------------|---------|
| 3/4"              | 0.00              | 0%                 | 0%                   | 100%                | 100     |
| 1/2"              | 152.60            | 5.04%              | 5.04%                | 94.96%              | 90-100  |
| 3/8"              | 806.90            | 26.67%             | 31.71%               | 68.29%              | 40-75   |
| 4                 | 1,766.10          | 58.37%             | 90.08%               | 9.92%               | 5-25    |
| 8                 | 252.40            | 8.34%              | 98.43%               | 1.57%               | 0-10    |
| 16                | 18.10             | 0.60%              | 99.02%               | 0.98%               | 0-5     |
| 200               | 2.60              | 0.09%              | 99.11%               | 0.89%               | Max 1.5 |
| FONDO             | 26.90             | 0.89%              | 100.00%              | 0.00%               |         |
| GRUMOS            | 0.00              | 0.00%              |                      |                     |         |
| TOTAL             | 3,025.60          |                    |                      |                     |         |

|                   |      |
|-------------------|------|
| MODULO DE FINURA: | 6.24 |
|-------------------|------|

## CURVA GRANULOMÉTRICA

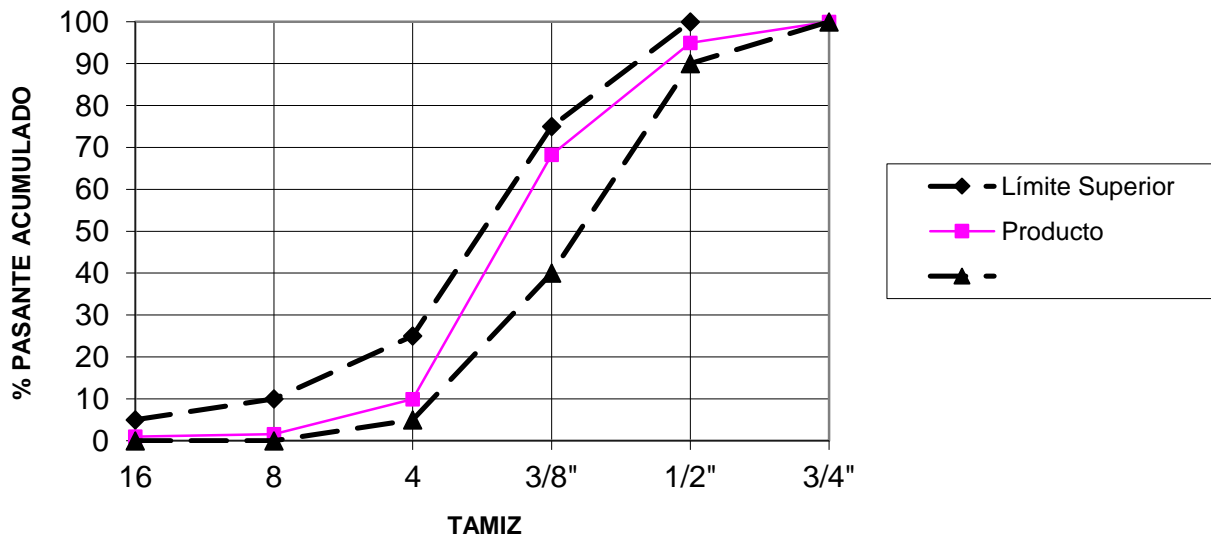

OBSERVACION: ( % MAT. LIVIANO = 0,16 ) ( % CHERT = 3,36 ) ( ARCILLA = 0,10 )

Sr. E. Wandemberg  
LABORATORISTA